




Machine-Learning Assisted Exploration: Toward the Next-Generation Catalyst for Hydrogen Evolution Reaction

Sichen Wei,¹ Soojung Baek,¹ Hongyan Yue,² Maomao Liu,³ Seok Joon Yun,⁴ Sehwan Park,⁴ Young Hee Lee,⁴ Jiong Zhao,⁵ Huamin Li,^{3,z} Kristofer Reyes,^{1,z} and Fei Yao^{1,z} 

¹Department of Materials Design and Innovation, University at Buffalo, Buffalo, New York 14260, United States of America

²School of Materials Science and Engineering, Harbin University of Science and Technology, Harbin 150040, People's Republic of China

³Department of Electrical Engineering, University at Buffalo, Buffalo, New York 14260, United States of America

⁴Center for Integrated Nanostructure Physics, Institute for Basic Science, Department of Energy & Department of Physics, Sungkyunkwan University, Suwon, Gyeonggi-do 16419, Republic of Korea

⁵Department of Applied Physics, Hong Kong Polytechnic University, Hung Hom, CD 612, Kowloon, Hong Kong, Hong Kong Special Administrative Region of China, People's Republic of China

The development of active catalysts for hydrogen evolution reaction (HER) made from low-cost materials constitutes a crucial challenge in the utilization of hydrogen energy. Earth-abundant molybdenum disulfide (MoS₂) has been discovered recently with good activity and stability for HER. In this report, we employ a hydrothermal technique for MoS₂ synthesis which is a cost-effective and environmentally friendly approach and has the potential for future mass production. Machine-learning (ML) techniques are built and subsequently used within a Bayesian Optimization framework to validate the optimal parameter combinations for synthesizing high-quality MoS₂ catalyst within the limited parameter space. Compared with the heavy-labor and time-consuming trial-and-error approach, the ML techniques provide a more efficient toolkit to assist exploration of the most effective HER catalyst in hydrothermal synthesis. To investigate the structure-property relationship, scanning electron microscope (SEM), transmission electron microscope (TEM), X-ray diffraction (XRD), Raman spectroscopy, X-ray photoelectron spectroscopy (XPS), and various electrochemical characterizations have been conducted to investigate the superiority of the ML validated optimized sample. A strong correlation between the material structure and the HER performance has been observed for the optimized MoS₂ catalyst.

© 2021 The Author(s). Published on behalf of The Electrochemical Society by IOP Publishing Limited. This is an open access article distributed under the terms of the Creative Commons Attribution 4.0 License (CC BY, <http://creativecommons.org/licenses/by/4.0/>), which permits unrestricted reuse of the work in any medium, provided the original work is properly cited. [DOI: 10.1149/1945-7111/ac41f1]



Manuscript submitted September 22, 2021; revised manuscript received November 17, 2021. Published December 22, 2021. *This paper is part of the JES Focus Issue on Women in Electrochemistry.*

Supplementary material for this article is available [online](#)

The ever-increasing demand for energy consumption and harmful CO₂ emission necessitate the urgent need for clean energy. As an eco-friendly fuel with the highest gravimetric energy density, the widespread adoption of hydrogen fuel will reduce energy-related emissions and improve energy efficiency.^{1–4} Hydrogen can be produced by electrochemical water splitting. Achieving high-efficiency water splitting requires the use of a catalyst to minimize the overpotential to drive the hydrogen evolution reaction (HER).^{5–9} Pt-group metals (PGM) are excellent catalysts for HER, but their practical applications are limited by the high cost and scarcity.^{10–14} Therefore, the development of active HER catalysts made from low-cost materials constitutes a crucial challenge in the utilization of hydrogen energy. Recently, earth-abundant two-dimensional (2D) transition metal dichalcogenides (TMDs) have been discovered and demonstrated enormous potentials in various energy-related applications including energy storage, catalysis, electronic devices, and biosensors.^{15–18} Among them, molybdenum disulfide (MoS₂) has been proved with outstanding catalytic activity and stability for HER.^{19–23} MoS₂ can be prepared by various techniques including wet chemical synthesis, physical and chemical vapor deposition.^{24–28} Nevertheless, the above-mentioned methods normally involve the use of toxic reactants and complicated processes which are not environment friendly and cost-effective.

On the other hand, Machine-Learning (ML) technique has been identified as an effective approach to facilitate material exploration. For example, Kaxiras's group²⁹ employed a data-driven approach to investigate the magnetic properties of different A₂B₂X₆ monolayer structures considering the total energy, magnetic order, magnetic moment, and magnetic excitation energy. Fyta et al.³⁰ exploited an ML approach to evaluate the lithium adsorption free energy on

TMDs which was found to be dominated by the lowest unoccupied state of the substrate. In their report, a set of descriptors were constructed and the adsorption energy of different alkali metals on different TMDs was successfully predicted with the help of ML. Such data-driven methods are amenable when there exists a large body of existing reliable data to which we can fit ML models with a high degree of fidelity. However, in many instances, such data is sparse and expensive to obtain experimentally. Closed-loop design and Bayesian methods, such as Active Learning and Bayesian Optimization (BO)³¹ can be utilized to mitigate this problem. BO has been shown effective in the optimization of many materials systems, including optimizing chemical synthesis,^{32,33} synthesis of quantum dots,³⁴ and phase-change memory nanocomposites,³⁵ to name a few examples. When dealing with a particular device application (such as catalysis) involving novel material development, however, their limitation is exacerbated by the fact that the link to be established, namely that between synthesis parameters to device performance spans the synthesis-material-device scale, meaning statistical correlations inferred between a limited set of synthesis conditions and corresponding device performance metrics are diluted. In addition, multi-objective characterizations of device performance also led to further difficulty in the optimization problem.

Herein, we aim to employ an aqueous-based hydrothermal synthesis technique which is an environmentally friendly and cost-effective approach to achieve high-performance MoS₂ HER catalysts. Six sets of initial manually designed synthesis were conducted and one was identified with better HER performance in terms of both overpotential and the Tafel slope. To further improve the HER performance, the synthesis condition needs to be further optimized. Before further exploring the vast parameter space, it is necessary to first validate the current manually picked synthesis parameters representing the local optimality within the explored space in the

^zE-mail: huaminli@buffalo.edu; kreyes3@buffalo.edu; feiyao@buffalo.edu

specific range considering the large parameter-selection intervals. Therefore, we investigated how to use a closed-loop design in an extreme case to perform an extremely limited, criteria-based exploration of synthesis conditions space to validate manually discovered optimized synthesis parameters. Specifically, a Gaussian Process (GP) belief model was built to map the hydrothermal synthesis conditions to a corresponding figure of merit for HER performance. The GP belief model was then used the BO algorithm to suggest the next set of synthesis conditions, which were then used to synthesize a new MoS₂ sample. After characterizing the HER activity of the sample, the GP beliefs were updated using Bayesian statistics, and the updated posterior beliefs were used to initiate the next iteration of the closed loop. Through executing this closed loop several times within a limited iteration budget, we can more effectively validate extant optimal conditions than compared to a coarse grained, non-optimization-oriented design under similar experimental budgets. As a result, the BO algorithm validated the optimized MoS₂ sample exhibited the best HER performance in terms of overpotential and Tafel slope. The origin of the better HER activity compared to the other samples can be attributed to the fast ion transport associated with the enlarged interlayer space and the increased number of potential active sites for HER originated from the increased surface area.

Experimental Section

Materials and synthesis.—MoS₂ samples were synthesized by a hydrothermal technique using ammonium molybdate and thiourea (Fisher Scientific, USA) as precursors. Specifically, ammonium molybdate and thiourea were dispersed in DI water followed by vigorously stirring until the solids were completely dissolved and a transparent solution was obtained. The solution was then transferred into a 100 ml Teflon line autoclave and heated in a convection oven. The reaction conditions were manually selected for the initial design of synthesis. Specifically, the temperature was set between 180 °C and 205 °C. The reaction time was varied from 16 to 26 h. The Mo and S precursor concentrations were selected between 0.02 ~ 0.03 mol l⁻¹ and 0.65 to 0.9 mol l⁻¹ with a step variation of 0.002 and 0.05 mol l⁻¹, respectively. The solution was then naturally cooled down to room temperature after reaction and the precipitate was collected by centrifugation and washed using DI water and ethanol for three times each. The final product was then dried in a vacuum oven overnight at 60 °C. The details for manually designed synthesis conditions are listed in Table SI (available online at stacks.iop.org/JES/168/126523/mmedia).

Characterization.—The morphology and composition of all products were investigated by field-emission scanning electron microscope (FE-SEM) and energy dispersive X-ray (EDS) (Carl Zeiss AURIGA CrossBeam with Oxford EDS system). The transmission electron microscopy (TEM) was conducted using the JEM ARM 200 F system. X-ray diffraction and Raman spectroscopy were performed using a Rigaku Ultima IV with Cu K α radiation (wavelength at 1.541 nm) and Renishaw InVia with an excitation laser wavelength of 514 nm, respectively. X-ray photoelectron spectroscopy (XPS) is performed using a monochromatic Al K α source ($h\nu = 1486.6$ eV, ESCALAB 250, Thermo Scientific). Brunauer–Emmett–Teller (BET) specific surface area was measured on the Micromeritics Tri-Star II system by nitrogen (N₂) adsorption-desorption isotherm at 77 K.

Electrochemical measurement.—The ink for the HER test was prepared by dissolving 10 mg of as-prepared MoS₂ in a mixture of 500 μ l of ethanol, 500 μ l of DI water, and 15 μ l Nafion D-521 solution. The electrochemical characterization was performed using CHI760E electrochemical workstation (CH Instrument) in a standard three-electrode configuration which consists of a silver/silver chloride (Ag/AgCl in 1 M KCl), a platinum (Pt) wire, and an ink-coated glassy carbon rotating ring disc electrode as reference,

counter and working electrodes, respectively. The reference electrode was converted to the potential vs E_{RHE} based on the equation: $E_{RHE} = E_{Ag/AgCl} + 0.059 \text{ pH} + E^{\circ}_{Ag/AgCl}$, where $E^{\circ}_{Ag/AgCl} = 0.222$ V. The loading amount of MoS₂ catalyst is 0.285 mg cm⁻² and the samples were cycled 20 times before any data recording. Nitrogen gas saturated 0.5 M H₂SO₄ was employed as electrolyte. The linear sweep voltammetry (LSV) was carried out at a scan rate of 5 mV s⁻¹ and the built-in IR compensation was executed prior to LSV tests. The electrochemical impedance spectroscopy (EIS) was tested from 0.1 Hz to 1 MHz at an overpotential of 250 mV. For each sample, the cyclic voltammetry (CV) was carried out in a series of scan rates (20, 40, 50, 60, 80, and 100 mV s⁻¹) in the potential range of 0.05 ~ 0.15 V vs RHE. The double-layer capacitance (C_{dl}) was assessed from the slope of the linear regression between the current density differences ($\Delta J/2 = (J_{anode} - J_{cathode})/2$) at an overpotential of 0.1 V vs RHE) vs the scan rates. The accessible surface area of as-synthesized samples could be approximated from the electrochemical active surface area (ECSA). The ECSA was determined by $ECSA = C_{dl}/C_s$, where C_s stands for the specific capacitance of standard electrode materials on a unit surface area. Here, based on the literature reported C_s values for flat surfaces, 0.04 mF cm⁻² was used for ECSA calculations.³⁶ The turnover frequency (TOF) was calculated from CV measurement. The CV curve was measured in phosphate buffer solution (pH = 7) at a scan rate of 50 mV s⁻¹. The TOF was then calculated following the equation: $TOF = I/2Fn$, where I is the current from the polarization curve, F is the Faradic constant and n is the number of active sites. Among them, the n can be estimated using the relationship: $n = Q/2F$, where Q is the voltammetric charges and F is the Faradic constant, respectively.

Machine learning theory.—Closed-loop Bayesian exploration of synthesis conditions was performed to validate the optimality of the manually selected model within a limited experimental budget. Six batches of MoS₂ synthesis conditions (Mo and S precursor amount, temperature, and reaction time) and the corresponding HER activity (evaluated by overpotential at the current level of 10 mA cm⁻², *i.e.*, η_{10} , and the Tafel slope) were used (see Table SI) to train Gaussian Process (GP) belief model to express a scalar combination of the electrochemical responses as a function of input synthesis conditions. Implicit in this modeling is that the material precursors, apart from the concentration, remain constant throughout the campaign. This technique can be adapted to learning optimal synthesis conditions and choice of material, given an appropriate parameterization of material properties as additional features or inputs to the ML model. The GP was fit to these first six “seed” data points, resulting in a Bayesian prior GP, B^6 . We then selected experiments based on this prior, according to one of several decision-making policies such as the Expected Improvement (EI), Upper Confidence Bound (UCB), Maximum Variance (MV), Exploration, and Exploitation policies. A full derivation of the policies is provided in the Supplemental Information. Broadly speaking, EI, UCB, and Exploitation policies are those geared toward optimization, while MV and Exploration are policies meant for generally learning the response function. In general, the policies would score potential experiments based on GP beliefs and some measure of information gain. The experiments with maximal scores were selected. We refer the reader to the Supplementary Information for more details.

Prior to running the physical, closed-loop experimental campaign, we performed simulations of this campaign to assess model and policy performance for the given problem. From the prior B^6 , we sampled a surrogate for the ground truth response function $f_i^* \sim B^6$. We then selected an experiment according to some policy $x^7 = \text{argmax}_x a(x; B^6)$, and then simulated a noisy observation of the ground truth:

$$y_7 = f_i^*(x^7) + W,$$

where W is sampled from $N(0; \sigma_w^2)$. This is used to form the simulated posterior belief B^7 , which was subsequently treated as the prior belief for the next iteration of the closed loop. By iterating through this loop several times, we simulated an experimental campaign. We then simulated 100 such campaigns, each with different surrogates of the ground truth, f_1^*, \dots, f_{100}^* . We then aggregated simulation results to calculate a performance metric called relative Opportunity Cost (OC), which is a relative measure of how optimal the predicted optimum synthesis conditions are compared to the true optimal conditions, with smaller OC values implying more optimal predictions.

Results and Discussion

Initial manual design of synthesis and performance evaluation for aqueous-based MoS₂ catalyst.—We employed a hydrothermal technique for MoS₂ synthesis where ammonium molybdate and thiourea were used as Mo and S precursors, respectively. Such a method involves no use of toxic reactants and therefore has a potential for large-scale adoption due to its environmentally friendly and cost-effective nature. The initial design of synthesis conditions was manually picked based on our experimental experiences in hydrothermal synthesis and each parameter was confined in a specific range, as shown in Table SI. Six batches of manually designed samples were labeled as MoS₂-1 to MoS₂-6 and the corresponding HER activities were evaluated by LSV measurements, as shown in Fig. 1a. The values of η_{10} were extracted from the polarization curves which are 288, 243, 240, 254, 254, and 249 mV for sample MoS₂-1 to MoS₂-6, respectively (see Table SI). It is clear to see that MoS₂-3 exhibited the smallest η_{10} value, indicating a better HER activity compared to the rest of the manually designed samples.

As a multistep reaction, HER starts with Volmer reaction ($H_3O^+ + e^- \rightarrow H^* + H_2O$), and the intermediate (adsorbed H^*) is desorbed from the catalyst surface by either Tafel reaction ($H^* + H^* \rightarrow H_2$) or Heyrovsky reaction ($H_3O^+ + H^* + e^- \rightarrow H_2 + H_2O$) in acidic media. The values of the Tafel slope can be used to identify the rate-determine step.^{37,38} The Tafel slopes are plotted in Fig. 1b and the related values are summarized in Table SI. Except for MoS₂-1 which showed a poor HER performance, all of the other samples showed the Tafel slope value in the range of 60 ~ 80 mV dec⁻¹, suggesting that Heyrovsky reaction was the rate-determine step. The slow Heyrovsky reaction can be ascribed to the large MoS₂ resistance resulting in a limited number of electrons that can be transferred to the catalyst/electrolyte interface. The EIS measurement was carried out to investigate the charge transfer resistance. The resulting Nyquist plots of each sample are shown in Fig. 1c, where the charge transfer resistance (R_{ct}) governed HER kinetics can be evaluated by the radius of the semicircle. Smaller R_{ct} values were observed for MoS₂-3 (31.0 Ω) and MoS₂-6 (48.8 Ω). Considering the values of both overpotential

and Tafel slope, we observed generally better HER performance for MoS₂-3 among the manually designed 6 synthesis conditions.

Prior policy assessment through simulations.—Since the initial 6 batches of synthesis were fully determined by the experimentalists' experience and intuition, potentially superior synthesis conditions may exist but were not chosen by the experimentalists in the initial manual design process. To evaluate the optimality of MoS₂-3, we performed a limited BO to discover potentially superior synthesis conditions. In BO, decision-making policies allocate a small number of experiments between exploring the parameter space and focusing on regions believed to yield promising results, based on a limited understanding of the landscape it is exploring. This is called the exploration vs exploitation trade-off, and policies that perform this balance well typically are able to identify optima in fewer experiments than trial-and-error or grid-based search approaches.^{39,40}

In the past, BO has been used to efficiently explore synthesis parameter space in order to optimize chemical and material properties.^{34,41} In these past applications, the BO was executed on a relatively large number (50 – 100 s) of experiments executed by autonomous platforms. In this current setting, however, due to the non-autonomous, manual work and time needed to execute the synthesis and characterization of electrochemical performance, validation of MoS₂-3 is limited to a small number (less than 10) of experiments. In addition, the characterization spans from synthesis and processing parameters of material to device performance, requiring the optimization of several electrochemical quantities.

In this limited application, we utilized BO techniques to simply evaluate the optimality of MoS₂-3 with the goal of exploring parameter space in an objective-driven manner as much as possible. That is, given the prior results provided by MoS₂-3, we wish to utilize BO methods as a systematic way of validating its quality given the limited experimental budget, in contrast to further ad hoc search. We performed a Bayesian sequential design of experiments using GP belief models and the decision-making policies outlined in the above section. GP beliefs were fit to the initial seed data set of 6 synthesis conditions, and a decision-making policy would select an experiment to run based on these beliefs. Once the experiment was run, electrochemical performance was evaluated, the results of which were used to update the GP beliefs. This process would be repeated until the small experimental budget was expended. To select a specific decision-making policy to use during this validation campaign, we ran several simulations of the campaign. The use of such statistical simulation to perform meta-decision-making regarding policy and modeling choices has been shown effective in the past.^{42–44} We calculated OC curves for all four policies, which are shown in Fig. 2a. From this simulation study, we observed that the UCB policy had the best simulated performance.

Parameter space exploration.—To quantify the effectiveness of the ML-guided closed-loop exploration campaign in exploring synthesis parameter space, we calculated a data-spread metric.

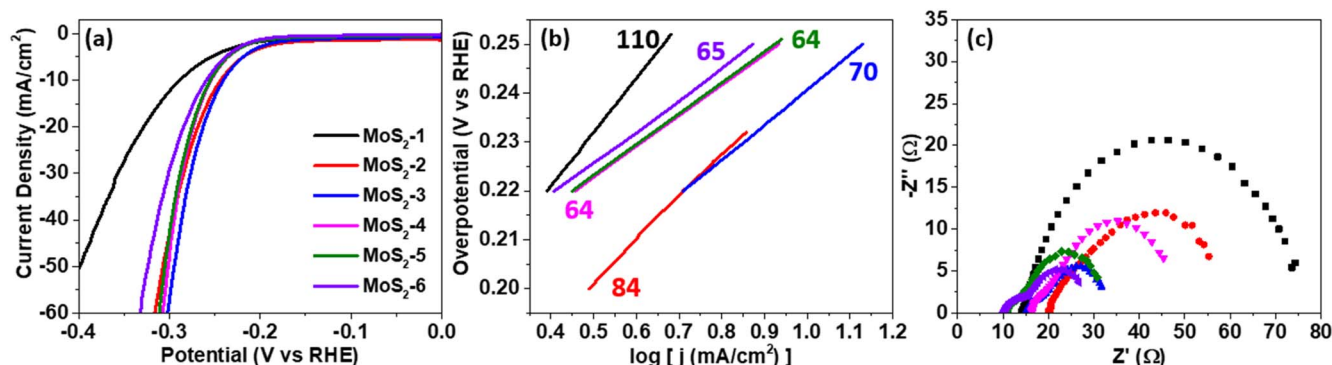


Figure 1. (a) The polarization curves, (b) the Tafel slopes, and (c) the Nyquist plot of the first 6 batches of manually designed MoS₂ samples.

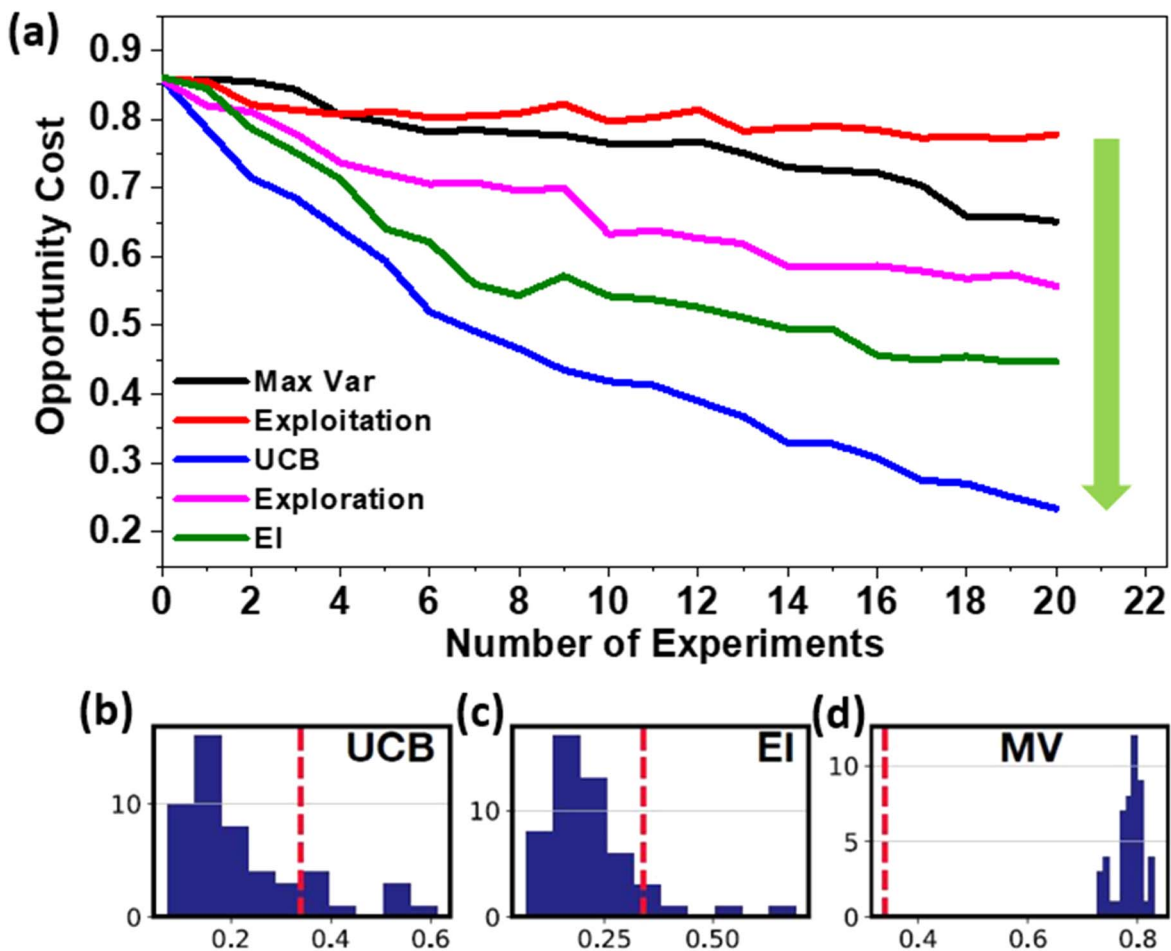


Figure 2. (a) Simulation results based on the validation campaign. These plots show a measure of policy performance, OC, as a function of the number of simulated experiments. Of the five policies evaluated, the UCB policy had the best simulated performance. (b)–(d) Mean distance from centroid distribution under simulated campaigns using the (b) UCB, (c) EI, and (d) MV. The dashed red line indicates the actual distance (0.34) calculated from the physical experimental campaign. We observe that the distance from centroid is larger than a majority of those obtained under simulated UCB and EI policies, while lower than those obtained under the simulated MV policy, suggesting that the physical campaign robustly explored space to look for high performing synthesis conditions.

Specifically, for a set of data points $X = \{x_i\}$, we calculate the mean distance from the centroid

$$s(X) = \frac{1}{|X|} \sum_{i=1}^{|X|} x_i - \mu(X)_2,$$

where $\mu(X)$ is the centroid of the data points X and it is a measure of the spread of the data.

$$\mu(X) = \frac{1}{|X|} \sum_{i=1}^{|X|} x_i.$$

Figures 2b–2d plots the distribution of this spread over simulated experimental campaigns using the UCB, EI, and MV policies. In addition, this statistic was calculated for the actual campaign data, $s_{\text{data}} = 0.34$. We plot this value as a vertical red dashed line. Examining the plots, we show that the spread for the actual data is larger than a majority of the simulated spreads using both the EI and UCB policies, indicating that the experimental campaign was able to explore well within the limited set of experiments available to it. As expected, the MV policy does explore more, as indicated by the larger spread values. This, along with the simulation results in Fig. 2a, indicates that balanced decision-making policies such as EI and UCB consistently outperform more exploration-oriented policies

such as MV in finding optima within a small number of experiments. More discussion can be found in Supporting Information.

The sequential study based on BO predictions was performed and after 10 steps of the study, a final predicted condition was given. The samples were synthesized correspondingly and the synthesis conditions for each step can be found in Table SI. Surprisingly, we found that the synthesis condition predicted by the BO algorithm for the optimized MoS_2 catalyst (labeled as $\text{MoS}_2\text{-Opt}$) is very similar to that of $\text{MoS}_2\text{-3}$, which has been identified as a better HER catalyst compared to the other samples synthesized by initial manually selected conditions. As a result, the BO algorithm has determined that a synthesis condition close to $\text{MoS}_2\text{-3}$ can yield the promising HER activity after the step-wise study.

The campaign shows the viability of such techniques in systematically verifying the performance of $\text{MoS}_2\text{-3}$ in a limited experimental setting. BO is one of the limited techniques that can operate in this few-shot environment.⁴⁵ This process can be accelerated to some degree through the inclusion of informative priors for the GP model, which can come from related systems⁴⁶ or elicited directly from domain experts.⁴⁷ By augmenting the above procedure with such methods, we can overcome the experimental limitations for a more effective search.

Experimental validation.—To validate the BO algorithm predictions, HER activities of different MoS_2 samples synthesized at ML-predicted conditions (labeled as $\text{MoS}_2\text{-Px}$, where Px indicates

the predicated batch number) were investigated using electrochemical techniques and the related results were summarized in Table SI. HER performance for selected representative samples (i.e. MoS₂-P3, MoS₂-P9, and MoS₂-Opt) is shown in Fig. 3. In Fig. 3a, the MoS₂-Opt exhibits a small η_{10} of 240 mV and a Tafel slope of 64 mV dec⁻¹, which is very close to that of MoS₂-3 (243 mV, 70 mV dec⁻¹), demonstrating good reproducibility of these two synthesis conditions. The overpotentials and Tafel slopes for MoS₂-P3 and MoS₂-P9 were 219 mV, 88 mV dec⁻¹, and 253 mV, 72 mV dec⁻¹, respectively. Considering the HER performance is evaluated in terms of both overpotentials and Tafel slopes, the overall HER activity of MoS₂-Opt outperformed the rest of the ML-predicted samples. Although MoS₂-P3 has a smaller η_{10} , a larger Tafel slope compared to MoS₂-Opt makes it unfavorable as an efficient HER electrocatalyst. Furthermore, MoS₂-Opt displayed a smaller R_{ct} of 49 Ω compared to that of MoS₂-P3 (60 Ω) and MoS₂-P9 (50 Ω) (see Fig. 3c, suggesting its fast charge transport at the catalyst/electrolyte interface and therefore a good HER activity. In addition, the polarization curves of the MoS₂-Opt before and after 1000 CV cycles at a scan rate of 50 mV s⁻¹ showed negligible degradation as shown in Fig. 3d, demonstrating outstanding long-term stability of the BO-predicted optimized MoS₂ sample.

To gain insight into the origin of the better HER performance in the BO-predicted MoS₂-Opt, a series of characterizations were carried out. The morphology of the as-synthesized MoS₂-Opt was investigated using SEM and TEM. As shown in Fig. 4a, the

MoS₂-Opt exhibited a nanoflower-like structure with the tendency to form aggregated bundles. The TEM image shown in Fig. 4b confirmed the flower-shaped MoS₂ morphology assembled by wrinkled MoS₂ nanoflakes. The HRTEM analysis shown in Fig. 4c revealed that the MoS₂-Opt showed polycrystalline structure as evidenced by the clear ring patterns in the SAED pattern. Furthermore, 2H phase MoS₂ with trigonal prismatic coordination was observed, as shown in Fig. 4d. The corresponding EDS elemental mapping of Mo, S, and O in Figs. 4e–4h revealed a uniform distribution of Mo and S, indicating the successful formation of MoS₂. The emerging of oxygen signals in the EDS mapping can be ascribed to the sample oxidation after preparation.

It is well known that the HER performance of 2H phase MoS₂ is inferior to that of 1T MoS₂ due to its semiconducting nature. The relatively large electrical resistance in 2H MoS₂ will hinder the electron transport to catalyst/electrolyte interface and thus large R_{ct} values and slow Heyrovsky reaction can be expected. This eventually leads to relatively poor HER catalytic activity in all of our aqueous-based samples. Nevertheless, the introduction of metallic 1T MoS₂ normally requires toxic organic reactants and complicated process control,^{48–50} which re-emphasizes the importance of the current work with the focus of achieving a high-performance, PGM-free HER catalyst via a green synthesis process.

The chemical composition of the optimized sample was investigated using XPS, as shown in Fig. 5a. The complete survey spectrum of MoS₂-Opt showed the typical MoS₂ bonding

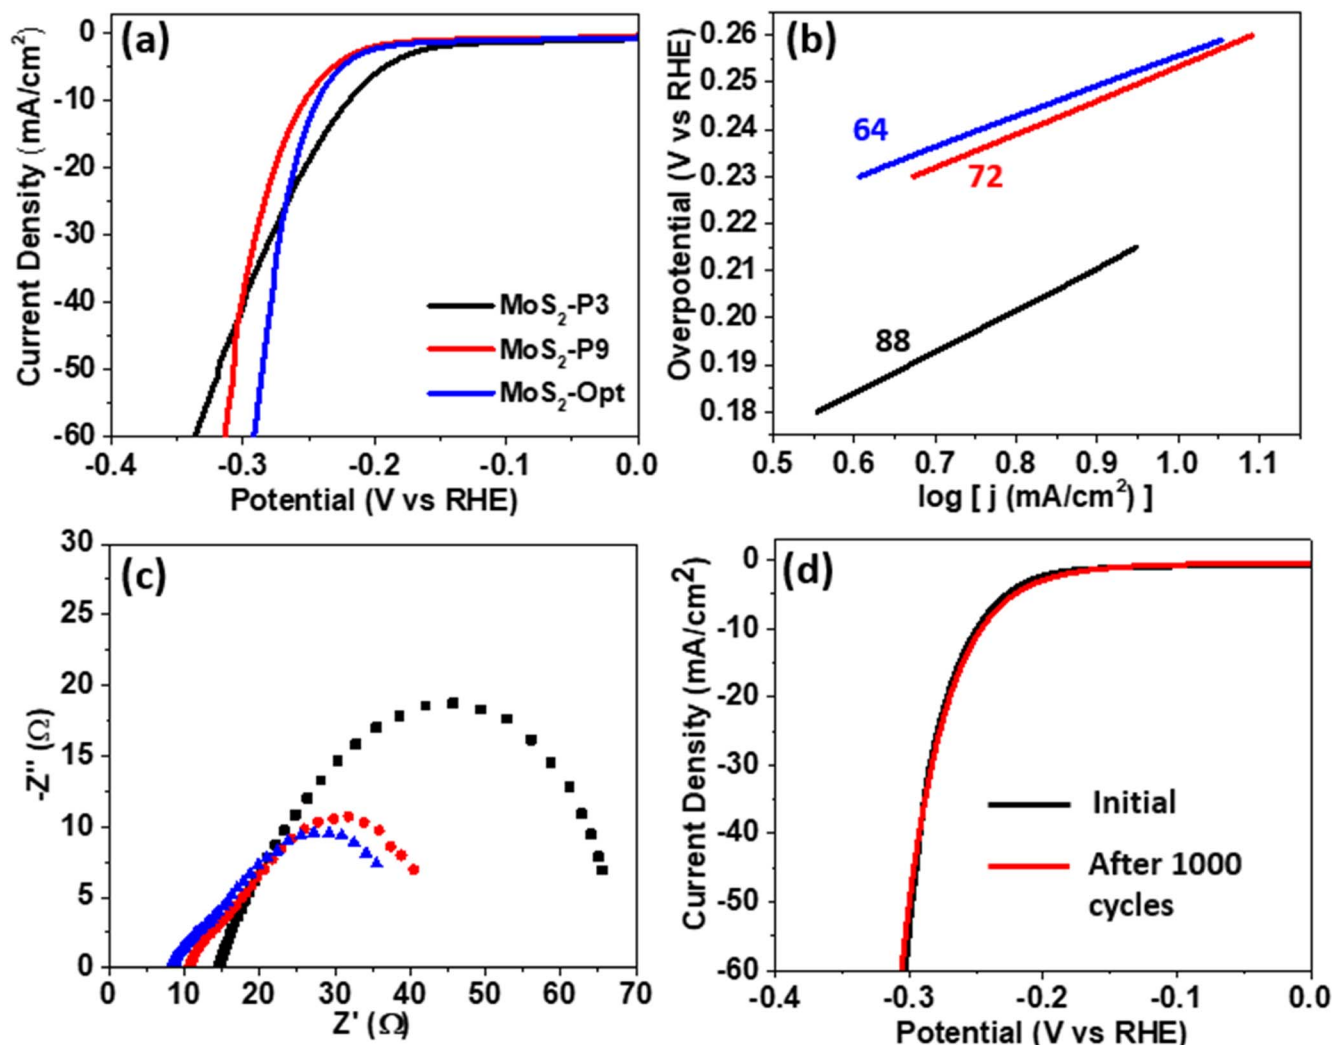


Figure 3. (a) Polarization curves, (b) Tafel plots, and (c) Nyquist plots of the selected ML-predicted samples. (d) The polarization curves of MoS₂-Opt before and after 1000 cycles of CV scan.

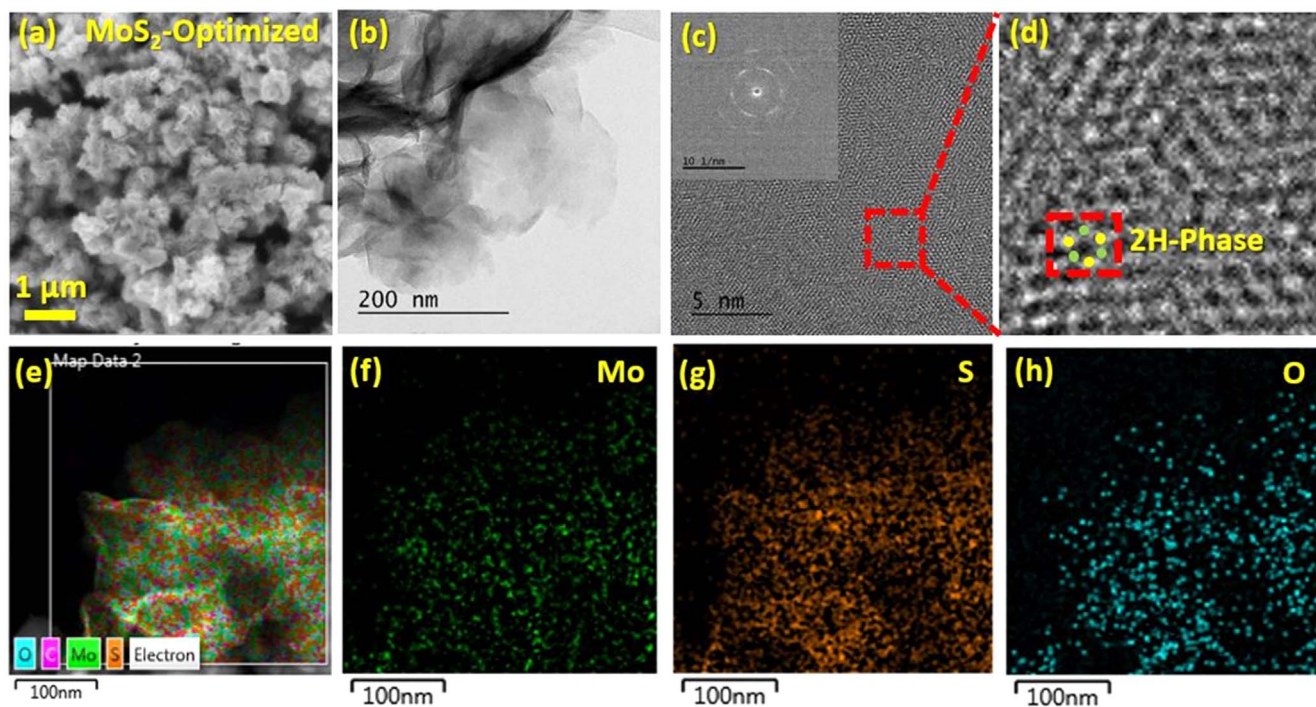


Figure 4. (a) SEM and TEM images for the MoS₂-Opt sample. (c) HRTEM image and corresponding SEAD pattern. (d) HRTEM image of the enlarged area in (c). The 2H phase atomic arrangement was marked in color. (e)–(h) EDS mapping of Mo, S, and O.

information with characteristic signals for Mo 3d and S 2p, which is consistent with the previous reports.^{51,52} The O 1s peak was also observed due to the unavoidable oxidation of the sample. Two major peaks located at ~ 228.5 and 231.7 eV can be found in Mo 3d spectrum in Fig. 5b which can be assigned to the Mo⁴⁺ 3d_{5/2} and Mo⁴⁺ 3d_{3/2}, respectively, with an S 2s peak at ~ 225.6 eV. As for the S 2p spectrum in Fig. 5c, doublet peaks are found at ~ 161.3 and 162.4 eV corresponding to the S 2p_{3/2} and S 2p_{1/2} peaks, respectively. The Mo 3d and S 2p peaks for all the samples correspond well with the previous reports,^{51,52} proving the successful formation of MoS₂. In addition, the deconvoluted spectrum for S 2p showed one set of doublet peaks, indicating the as-prepared MoS₂ contained only 2H phase, resonating well with our TEM observations.^{53,54} The O 1s spectrum shown in Fig. 5d showed two peaks at 531 and 532 eV resulting from the bonding of Mo–O and adsorbed water, indicating the slight oxidation of the MoS₂ sample. XPS spectrum for MoS₂-P3 and MoS₂-P9 were shown in Figs. S1 and S2 and no obvious differences were found compared to MoS₂-Opt.

The crystal nature and interlayer spacing of different MoS₂ samples synthesized at ML-predicted conditions were investigated by XRD, as shown in Fig. 5e. The peaks at 14.6° , 32.3° , and 57.3° can be ascribed to (002), (100), and (110) crystal planes of the 2H phase, respectively, which are consistent with previous reports for MoS₂.⁵⁵ For MoS₂-P9 and MoS₂-Opt, a downshift of (002) peak from $\sim 14^\circ$ to $\sim 9^\circ$ along with the emerging of a new peak at 18° which corresponds to the (004) crystal plane was observed indicating an enlarged interlayer spacing.⁵⁶ The extracted interlayer distance for MoS₂-Opt, P9, and P3 are 0.94, 0.92, and 0.64 nm, respectively (see Table SII). The highest interlayer spacing value in MoS₂-Opt will not only provide a large surface area but also benefit ion diffusion for the HER process, which is the main reason for the observed better HER activity as shown in Fig. 3. Besides that, the average crystallite size was also extracted from the XRD (002) peaks based on the Scherrer equation. As a result, the average crystallite sizes of MoS₂-P3, MoS₂-P9, and MoS₂-Opt were calculated to be 1.97 nm, 6.4 nm, and 6.94 nm, respectively, which is consistent with the previously reported value.⁵⁷ Furthermore, typical E_{2g} and A_{1g} vibration peaks were observed in the Raman spectrum for all

samples, as can be seen in Fig. 5f. The result indicated that the as-synthesized aqueous-based MoS₂ samples are solely 2H phase which is in line with the TEM and XPS observations in Figs. 4d and 5c. Brunauer–Emmett–Teller (BET) analysis in Fig. S3 showed that MoS₂-Opt exhibited a larger specific surface area of $23.9 \text{ m}^2 \text{ g}^{-1}$ compared to the other ML-predicted samples (see Table SIII) which can be attributed to the enlarged interlayer spacing as observed in Fig. 5e. Furthermore, the pore size distribution was extracted by the Barrett–Joyner–Halenda method (BJH), as can be seen in Fig. S3b. All samples exhibit a sharp peak at ~ 5 nm and a broad peak at a range of $20 \sim 40$ nm, indicating a mesopore-enriched structure of as-prepared MoS₂. The large surface area associated with abundant mesopores and large interlayer distance will facilitate the ion diffusion toward the catalyst surface, leading to an enhanced HER activity. The accessible surface area of as-synthesized samples was evaluated by ECSA, as shown in Fig. S4. The C_{dl} and the corresponding ECSA were summarized and listed in Table SIV. The extracted ECSA of MoS₂-Opt is 929.1 cm^2 , which is the largest among all samples and resonates well with our observation in Fig. S3. The Turnover frequency of MoS₂-Opt was also extracted to be $0.042 \text{ H}_2/\text{s}$ at an overpotential of 100 mV, as can be seen in Fig. S5, which is corresponding to the previously reported value for MoS₂.^{20,58} Overall, the origin of the better HER performance observed in the MoS₂-Opt sample can be attributed to the increased interlayer space which facilitated the charge transfer at the electrode/electrolyte interface, and the enlarged surface area which increased the number of potentially HER active sites.

Conclusion

In summary, we employed an aqueous-based hydrothermal technique to synthesis MoS₂ as an alternative catalyst of PGM for hydrogen production. This method does not involve any toxic reactants or gases which is environmentally friendly and cost-effective. We used BO to validate and optimize the manually obtained high-performing MoS₂ sample. It is important to note that an exhaustive exploration of the parameter space is not the goal of BO. Instead, BO attempts to identify optimal parameters through a combination of exploration and exploitation. Within a small set of

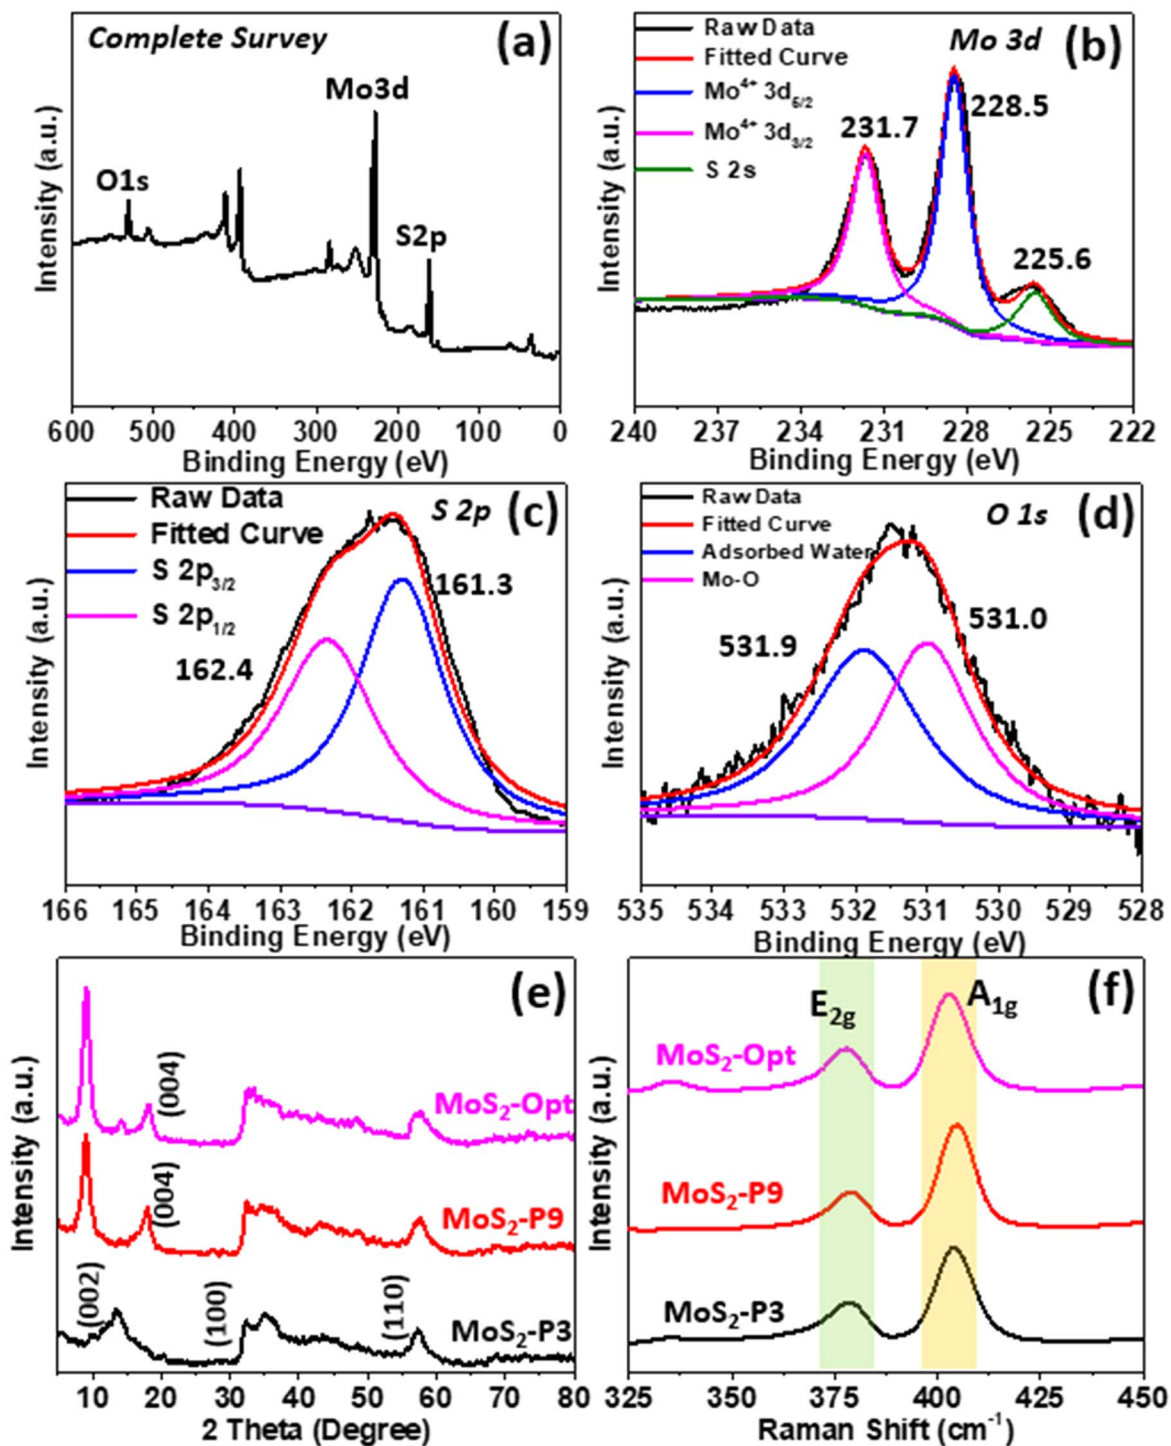


Figure 5. (a) The complete XPS survey spectrum for MoS₂-Opt, (b) the Mo 3d spectrum, (c) the S 2p spectrum, and (d) the O 1s spectrum. (e) The powder XRD pattern, (f) Raman spectra.

9 validation experiments selected through the UCB policy, we identified an optimized set of synthesis conditions (MoS₂-Opt) that, while resulting in better overall performance, are similar to those conditions in MoS₂-3. Note that this result does not imply that MoS₂-3 is globally optimal, which would require a larger set of experiments to be performed. Instead, the use of BO was meant to validate its optimality as much as possible within an extremely limited experimental budget, pointing to the potential of bootstrapping such ML methods to work, validate and improve manually identified synthesis conditions. Moreover, the catalysis performance

of as-synthesized MoS₂ is still inferior to the solvothermal synthesized MoS₂ due to the existence of pure 2H phase. To further improve the HER performance, structure engineering strategies including defect introduction, phase engineering, and composite formation will be utilized in the future.

Acknowledgments

This work was partially supported by New York State Energy Research and Development Authority (NYSERDA) under Award 138126, the National Science Foundation (NSF) under Award ECCS-

1944095, and the Brookhaven Science Associates LLC, Department of Energy, contract #84747. The authors acknowledge support from the Vice President for Research and Economic Development (VPRED) at the University at Buffalo.

ORCID

Fei Yao  <https://orcid.org/0000-0001-8414-7955>

References

- Y. Shi and B. Zhang, "Recent advances in transition metal phosphide nanomaterials: synthesis and applications in hydrogen evolution reaction." *Chem. Soc. Rev.*, **45**, 1529 (2016).
- Q. Li, B. Guo, J. Yu, J. Ran, B. Zhang, H. Yan, and J. R. Gong, "Highly efficient visible-light-driven photocatalytic hydrogen production of CdS-cluster-decorated graphene nanosheets." *J. Am. Chem. Soc.*, **133**, 10878 (2011).
- K. Zeng and D. Zhang, "Recent progress in alkaline water electrolysis for hydrogen production and applications." *Prog. Energy Combust. Sci.*, **36**, 307 (2010).
- A. Kudo and Y. Miseki, "Heterogeneous photocatalyst materials for water splitting." *Chem. Soc. Rev.*, **38**, 253 (2009).
- Z. W. She, J. Kibsgaard, C. F. Dickens, I. Chorkendorff, J. K. Nørskov, and T. F. Jaramillo, "Combining theory and experiment in electrocatalysis: insights into materials design." *Science*, **355**, eaad4998 (2017).
- Y. Li, H. Wang, L. Xie, Y. Liang, G. Hong, and H. Dai, "MoS₂ nanoparticles grown on graphene: an advanced catalyst for the hydrogen evolution reaction." *J. Am. Chem. Soc.*, **133**, 7296 (2011).
- Y. Jiao, Y. Zheng, M. Jaroniec, and S. Z. Qiao, "Design of electrocatalysts for oxygen- and hydrogen-involving energy conversion reactions." *Chem. Soc. Rev.*, **44**, 2060 (2015).
- X. Zou and Y. Zhang, "Noble metal-free hydrogen evolution catalysts for water splitting." *Chem. Soc. Rev.*, **44**, 5148 (2015).
- J. Wang, W. Cui, Q. Liu, Z. Xing, A. M. Asiri, and X. Sun, "Recent progress in cobalt-based heterogeneous catalysts for electrochemical water splitting." *Adv. Mater.*, **28**, 215 (2016).
- J. Xie, H. Zhang, S. Li, R. Wang, X. Sun, M. Zhou, J. Zhou, X. W. Lou, and Y. Xie, "Defect-Rich MoS₂ ultrathin nanosheets with additional active edge sites for enhanced electrocatalytic hydrogen evolution." *Adv. Mater.*, **25**, 5807 (2013).
- M. A. Lukowski, A. S. Daniel, F. Meng, A. Forticaux, L. Li, and S. Jin, "Enhanced hydrogen evolution catalysis from chemically exfoliated metallic MoS₂ Nanosheets." *J. Am. Chem. Soc.*, **135**, 10274 (2013).
- E. J. Popczun, J. R. McKone, C. G. Read, A. J. Baciocchi, A. M. Wiltrout, N. S. Lewis, and R. E. Schaak, "Nanostructured nickel phosphide as an electrocatalyst for the hydrogen evolution reaction." *J. Am. Chem. Soc.*, **135**, 9267 (2013).
- M. S. Faber and S. Jin, "Earth-abundant inorganic electrocatalysts and their nanostructures for energy conversion applications." *Energy Environ. Sci.*, **7**, 3519 (2014).
- J. Wang, F. Xu, H. Jin, Y. Chen, and Y. Wang, "Non-noble metal-based carbon composites in hydrogen evolution reaction: fundamentals to applications." *Adv. Mater.*, **29**, 1605838 (2017).
- M. Chhowalla, H. S. Shin, G. Eda, L. J. Li, K. P. Loh, and H. Zhang, "The chemistry of two-dimensional layered transition metal dichalcogenide nanosheets." *Nat. Chem.*, **5**, 263 (2013).
- D. Jariwala, V. K. Sangwan, L. J. Lauhon, T. J. Marks, and M. C. Hersam, "Emerging device applications for semiconducting two-dimensional transition metal dichalcogenides." *ACS Nano*, **8**, 1102 (2014).
- C. Tan and H. Zhang, "Two-dimensional transition metal dichalcogenide nanosheet-based composites." *Chem. Soc. Rev.*, **44**, 2713 (2015).
- Q. Lu, Y. Yu, Q. Ma, B. Chen, and H. Zhang, "2D Transition-metal-dichalcogenide-nanosheet-based composites for photocatalytic and electrocatalytic hydrogen evolution reactions." *Adv. Mater.*, **28**, 1917 (2016).
- D. Voiry, J. Yang, and M. Chhowalla, "Recent strategies for improving the catalytic activity of 2D TMD nanosheets toward the hydrogen evolution reaction." *Adv. Mater.*, **28**, 6197 (2016).
- H. Li et al., "Activating and optimizing MoS₂ basal planes for hydrogen evolution through the formation of strained sulphur vacancies." *Nat. Mater.*, **15**, 48 (2016).
- J. D. Benck, T. R. Hellstern, J. Kibsgaard, P. Chakhranont, and T. F. Jaramillo, "Catalyzing the hydrogen evolution reaction (HER) with molybdenum sulfide nanomaterials." *ACS Catal.*, **4**, 3957 (2014).
- A. B. Laursen, S. Kegnæs, S. Dahl, and I. Chorkendorff, "Molybdenum sulfides—efficient and viable materials for electro- and photoelectrocatalytic hydrogen evolution." *Energy Environ. Sci.*, **5**, 5577 (2012).
- B. Hinnemann, P. G. Moses, J. Bonde, K. P. Jørgensen, J. H. Nielsen, S. Hørch, I. Chorkendorff, and J. K. Nørskov, "Biomimetic hydrogen evolution: MoS₂ nanoparticles as catalyst for hydrogen evolution." *J. Am. Chem. Soc.*, **127**, 5308 (2005).
- M. Xu, T. Liang, M. Shi, and H. Chen, "Graphene-like two-dimensional materials." *Chem. Rev.*, **113**, 3766 (2013).
- W. Zhou, Z. Yin, Y. Du, X. Huang, Z. Zeng, Z. Fan, H. Liu, J. Wang, and H. Zhang, "Synthesis of Few-Layer MoS₂ Nanosheet-Coated TiO₂ nanobelt heterostructures for enhanced photocatalytic activities." *Small*, **9**, 140 (2013).
- D. Merki and X. Hu, "Recent developments of molybdenum and tungsten sulfides as hydrogen evolution catalysts." *Energy Environ. Sci.*, **42**, 3878 (2011).
- X. Huang, Z. Zeng, and H. Zhang, "Metal dichalcogenide nanosheets: preparation, properties, and applications." *Chem. Soc. Rev.*, **42**, 1934 (2013).
- T. Stephenson, Z. Li, B. Olsen, and D. Mitlin, "Lithium ion battery applications of molybdenum disulfide (MoS₂) nanocomposites." *Energy Environ. Sci.*, **7**, 209 (2014).
- T. D. Rhone, W. Chen, S. Desai, S. B. Torrisi, D. T. Larson, A. Yacoby, and E. Kaxiras, "Data-driven studies of magnetic two-dimensional materials." *Sci Rep.*, **10**, 15795 (2020).
- M. Dou and M. Fyta, "Lithium adsorption on 2D transition metal dichalcogenides: towards a descriptor for machine learned materials design." *J. Mater. Chem. A*, **8**, 23511 (2020).
- J. Snoek, H. Larochelle, and R. P. Adams, "Practical Bayesian optimization of machine learning algorithms." *Proceedings of the 25th International Conference on Neural Information Processing Systems*, **2**, 2951 (2012).
- B. Burger et al., "A mobile robotic chemist." *Nature*, **583**, 237 (2020).
- A.-C. Bédard, A. Adamo, K. C. Aroh, M. Grace Russell, A. A. Bedermann, J. Torosian, B. Yue, K. F. Jensen, and T. F. Jamison, "Reconfigurable system for automated optimization of diverse chemical reactions." *Science*, **361**, 1220 (2018).
- R. W. Epps, M. S. Bowen, A. A. Volk, K. Abdel-Latif, S. Han, K. G. Reyes, A. Amassian, and M. Abolhasani, "Artificial chemist: an autonomous quantum dot synthesis bot." *Adv. Mater.*, **32**, 2001626 (2020).
- A. G. Kusne et al., "On-the-fly closed-loop materials discovery via bayesian active learning." *Nat. Commun.*, **11**, 5966 (2020).
- H. Deng, C. Zhang, Y. Xie, T. Tumlin, L. Giri, S. P. Karna, and J. Lin, "Laser Induced MoS₂/carbon hybrids for hydrogen evolution reaction catalysts." *J. Mater. Chem. A*, **4**, 6824 (2016).
- T. Shinagawa, A. T. Garcia-Esparza, and K. Takanabe, "Insight on tafel slopes from a microkinetic analysis of aqueous electrocatalysis for energy conversion." *Sci Rep.*, **5**, 13801 (2015).
- A. P. Murthy, J. Theerthagiri, and J. Madhavan, "Insights on tafel constant in the analysis of hydrogen evolution reaction." *J. Phys. Chem. C*, **122**, 23943 (2018).
- D. R. Jones, M. Schonlau, and W. J. Welch, "Efficient global optimization of expensive black-box functions." *J. Global Optim.*, **13**, 455 (1998).
- L. Pack Kaelbling, M. L. Littman, A. W. Moore, and S. Hall, "Reinforcement learning: a survey." *J. Artif. Intell. Res.*, **4**, 237 (1996).
- A. E. Gongora, B. Xu, W. Perry, C. Okoye, P. Riley, K. G. Reyes, E. F. Morgan, and K. A. Brown, "A bayesian experimental autonomous researcher for mechanical design." *Sci. Adv.*, **6**, eaaz1708 (2020).
- A. E. Gongora, K. L. Snapp, E. Whiting, P. Riley, K. G. Reyes, E. F. Morgan, and K. A. Brown, "Using simulation to accelerate autonomous experimentation: a case study using mechanics." *iScience*, **24**, 102262 (2021).
- R. W. Epps, A. A. Volk, K. G. Reyes, and M. Abolhasani, "Accelerated AI development for autonomous materials synthesis in flow." *Chem. Sci.*, **12**, 6025 (2021).
- Y. Wang, K. G. Reyes, K. A. Brown, C. A. Mirkin, and W. B. Powell, "Nested batch mode learning and stochastic optimization with an application to sequential multi-stage testing in materials science." *SIAM J. Sci. Comput.*, **37**, B361 (2015).
- Y. Wang, Q. Yao, J. T. Kwok, and L. M. Ni, "Generalizing from a few examples: a survey on few-shot learning." *ACM Comput. Surv.*, **53**, 1 (2020).
- R. Raina, A. Y. Ng, and D. Koller, "Constructing informative priors using transfer learning." *Proceedings of the 23rd international conference on Machine learning* 713 (2006).
- F. A. Moala and A. O'Hagan, "Elicitation of multivariate prior distributions: a nonparametric bayesian approach." *J. Stat. Plann. Inference*, **140**, 1635 (2010).
- D. Wang, X. Zhang, S. Bao, Z. Zhang, H. Fei, and Z. Wu, "Phase engineering of a multiphase 1T/2H MoS₂ catalyst for highly efficient hydrogen evolution." *J. Mater. Chem. A*, **5**, 2681 (2017).
- L. Jiang, S. Zhang, S. A. Kulinich, X. Song, J. Zhu, X. Wang, and H. Zeng, "Optimizing Hybridization of 1T and 2H Phases in MoS₂ monolayers to improve capacitances of supercapacitors." *Mater. Res. Lett.*, **3**, 177 (2015).
- Z. Liu, Z. Gao, Y. Liu, M. Xia, R. Wang, and N. Li, "Heterogeneous nanostructure based on 1T-Phase MoS₂ for enhanced electrocatalytic hydrogen evolution." *ACS Appl. Mater. Interfaces*, **9**, 25291 (2017).
- G. Li et al., "All the catalytic active sites of MoS₂ for hydrogen evolution." *J. Am. Chem. Soc.*, **138**, 16632 (2016).
- J. Xie, J. Zhang, S. Li, F. Grote, X. Zhang, H. Zhang, R. Wang, Y. Lei, B. Pan, and Y. Xie, "Controllable disorder engineering in oxygen-incorporated MoS₂ ultrathin nanosheets for efficient hydrogen evolution." *J. Am. Chem. Soc.*, **135**, 17881 (2013).
- Q. Liu et al., "Electron-Doped 1T-MoS₂ via interface engineering for enhanced electrocatalytic hydrogen evolution." *Chem. Mater.*, **29**, 4738 (2017).
- D. Wang, B. Su, Y. Jiang, L. Li, B. K. Ng, Z. Wu, and F. Liu, "Polytype 1T/2H MoS₂ heterostructures for efficient photoelectrocatalytic hydrogen evolution." *Chem. Eng. J.*, **330**, 102 (2017).
- J. Guo, X. Chen, Y. Yi, W. Li, and C. Liang, "Layer-controlled synthesis of graphene-like mos₂ from single source organometallic precursor for Li-Ion batteries." *RSC Adv.*, **4**, 16716 (2014).
- H. Dong, Y. Xu, C. Zhang, Y. Wu, M. Zhou, L. Liu, Y. Dong, Q. Fu, M. Wu, and Y. Lei, "MoS₂ nanosheets with expanded interlayer spacing for enhanced sodium storage." *Inorg. Chem. Front.*, **5**, 3099 (2018).
- L. Fei, S. Lei, W. B. Zhang, W. Lu, Z. Lin, C. H. Lam, Y. Chai, and Y. Wang, "Direct TEM Observations of growth mechanisms of two-dimensional MoS₂ flakes." *Nat. Commun.*, **7**, 12206 (2016).
- E. F. Jaramillo, K. P. Jørgensen, J. Bonde, J. H. Nielsen, J. Greeley, S. Hørch, and I. Chorkendorff, "Identification of active edge sites for electrochemical H₂ evolution from MoS₂ Nanocatalysts." *Science*, **317**, 100 (2007).